

Excitonic emission in the presence of a two dimensional electron gas: a microscopic understanding

Y. Yayon, M. Rappaport, V. Umansky and I. Bar-Joseph

Department of Condensed Matter Physics, The Weizmann Institute of Science, Rehovot 76100, Israel

The near- and far-field photoluminescence spectra of a gated two-dimensional electron gas have been measured. Spatial fluctuations in the electron density are found to be manifested as spatial fluctuations in the emission amplitude of the negatively charged exciton (X^-) and in the peak energy of the neutral exciton (X). Consequently, the far-field X^- spectrum is a homogeneously broadened Lorentzian, while the X lineshape exhibits substantial inhomogeneous broadening. We present a novel and simple technique to extract the electron density from the X^- spectrum. We show that width of the far-field X line is proportional to the electron density fluctuations; hence it can be used to characterize the inhomogeneity in the electron density.

PACS: 73.21.Fg, 78.55.Cr, 78.67.De, 71.35.-y

The photoluminescence (PL) spectrum of a low density two dimensional electron gas (2DEG) has been the subject of considerable interest in recent years. It is observed that at a certain critical density, which depends on sample parameters but is typically between $10^{10} - 10^{11} \text{ cm}^{-2}$, the spectrum abruptly changes, from a broad line at high densities to two narrow peaks at low densities. A number of spectroscopy experiments at zero and high magnetic fields have clearly shown that the two peaks are associated with the neutral (X) and negatively charged (X^-) excitons [1–3]. The X^- is formed by the binding of a photoexcited electron-hole pair to an electron of the 2DEG. When the electron density is decreased its relative intensity decreases, and the spectrum becomes dominated by the X line. It was found that the appearance of this excitonic spectrum is correlated with a rapid decrease in the 2DEG conductivity [2]. This drop in conductivity was theoretically predicted to mark the onset of strong localization: As the 2DEG density is decreased, it becomes ineffective in screening the potential fluctuations due to the remote ionized donors, and they grow substantially [4,5]. Consequently, the electrons become localized in those potential fluctuations, and their ability to screen is further reduced. It was suggested that this reduction in screening and the subsequent strong localization of the electrons, allowed the observation of excitons in the presence of the 2DEG [2]. This conclusion was corroborated by a near-field optical study, which has shown that the X^- intensity exhibits strong spatial fluctuations: regions with high (low) electron density give rise to a strong (weak) X^- signal [6].

Our goal in the present work is to establish a quantitative relation between the optical spectrum at low electron density and the properties of the 2DEG. We measure and carefully analyze both the near- and far-field PL spectra of a gated 2DEG. We find that the near-field X^- lineshape is a Lorentzian, with an amplitude that varies strongly between different points in the sample, but with a very narrow distribution of peak energies and widths. Consequently, the far-field X^- lineshape is a homoge-

neously broadened Lorentzian, with a numerator that is proportional to the average density. We show that one can easily determine the average electron density in this low density regime from the PL spectrum. The near-field spectra of the X , on the other hand, exhibit a broad distribution of peak energies. We show that there is a clear correlation between the 2DEG density fluctuations and those of the X peak energies: regions with high (low) electron density give rise to a high (low) X peak energy. Hence, we conclude that the electron density fluctuations are the origin of the inhomogeneous broadening of the far-field X peak. Thus, the far-field X width is a measure for the electron density fluctuations in the sample.

The sample we studied is a 20 nm GaAs quantum well (QW). A 3.6 nm Si doped donor layer with a density of $4 \times 10^{18} \text{ cm}^{-3}$ is separated from the QW by a 50 nm $\text{Al}_{0.36}\text{Ga}_{0.64}\text{As}$ spacer layer. The distance between the QW and the sample surface is 107 nm. A $2 \times 2 \text{ mm}^2$ mesa was etched, and ohmic contacts were alloyed to the 2DEG layer. A 4.5 nm PdAu semitransparent gate was evaporated on top of the sample. The ungated 2DEG density and mobility (after illumination) at 4.2 K are $2.2 \times 10^{11} \text{ cm}^{-2}$, and $3 \times 10^6 \text{ cm}^2/\text{V sec}$, respectively.

Near-field PL measurements were performed using a system, which is described in detail in Ref. [7]. It is a low temperature near-field scanning optical microscope (NSOM) that operates in the collection mode: the sample is illuminated uniformly by a single-mode fiber and the emitted PL is collected through a tapered Al-coated optical fiber tip. The tip clear aperture diameter and transmission were measured to be 200 nm and 10^{-3} , respectively. The spatial resolution was determined using a grating mask to be 180 nm. The tip is glued to a quartz tuning fork, and its piezoelectric signal is used to control the height of the tip above the sample surface at $\sim 10 \text{ nm}$ [8]. For the excitation we used a He:Ne laser at 632.8 nm. The collected PL was dispersed by a 0.5 m spectrometer and detected using a cooled CCD camera. The overall system spectral resolution is 0.038 nm.

Figure 1a shows two near-field PL spectra (thin lines)

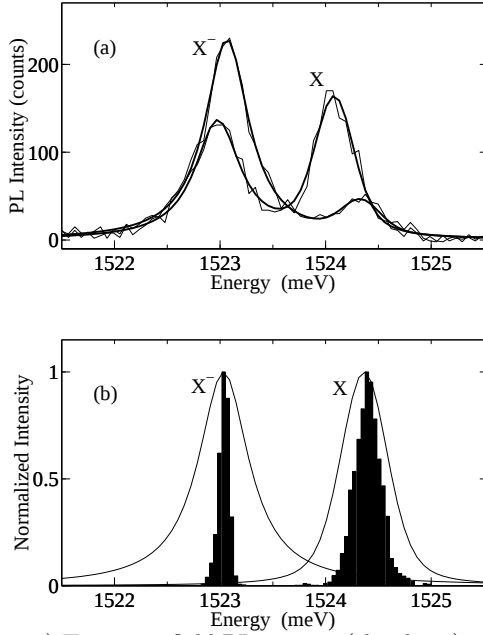


FIG. 1. a) Two near-field PL spectra (thin lines) and fitted curves (thick lines) at two points, $0.25 \mu\text{m}$ away from each other. b) Histograms of the peak energy of the X^- and X lines together with the fitted far-field lineshape for each excitonic line. The measurement is at a gate voltage that corresponds to $n_e = 3.1 \times 10^{10} \text{ cm}^{-2}$.

measured at a fixed gate voltage at two points in the sample, $0.25 \mu\text{m}$ apart. Both spectra consist of two peaks, X and X^- . It is seen that there are large differences between the two spectra over this small distance. The differences are manifested in the relative heights, widths and peak energies of each spectral line. The strong spatial fluctuations in the X^- intensity were already reported by us in a previous work [6]. We have significantly improved the signal to noise in the present measurements, and were thus able to better resolve the properties of the emission spectra. In extracting these properties we performed line fits at more than 3000 points in a scanned area of $4 \times 5.5 \mu\text{m}^2$, and repeated this procedure at three gate voltages. The thick lines in Fig. 1a are the fitted curves for the two spectra. The lineshape we used to fit each peak is a Voigt function, a convolution of a Lorentzian and a Gaussian, which describe homogeneous and inhomogeneous broadening, respectively. Such a lineshape was already used to fit the PL spectrum of an intrinsic sample, in which a 2DEG was created by optical excitation [9]. This is obviously a simplified lineshape, which neglects the contribution of high order effects. Nevertheless, we find that it gives a very good fit to the measured spectra. We obtained a significantly better fit at all points (nearly 10,000 in all measurements) using a Lorentzian-dominated Voigt lineshape for the X^- , with a negligible Gaussian width. The X line, on the other hand, is best described by a Voigt function with a significant inhomogeneous contri-

bution.

Let us examine the resulting properties of the X^- and X lineshapes. Figure 1b shows the normalized histograms of the peak energies at the ~ 3000 points for each excitonic line together with the normalized fitted far-field lineshapes. It can be clearly seen that the X^- peak energy is nearly independent of position with significantly less scatter than the far-field linewidth. We also find a very narrow distribution of the near-field X^- linewidth (not shown), with an average which is equal to the far-field width. We therefore conclude that the far-field X^- line is predominantly *homogeneously* broadened: It is a sum of many local Lorentzians, each having nearly the same peak energy and width but a different amplitude. This summation results in a far-field lineshape that is also a Lorentzian. The near-field X peak histogram, on the other hand, exhibits significantly greater scatter in its peak energies. This scatter is larger than the X homogeneous linewidth (Lorentzian width) and gives rise to *inhomogeneous* broadening of the X far-field spectrum. Indeed, we observe in Fig. 1b that the far-field X width is comparable to the X peak energy distribution. We find that the X peak is inhomogeneously broadened already in the near-field measurements. This implies that the broadening mechanism occurs on a length scale smaller than our spatial resolution, and the width of the X peak energy histogram measured at higher spatial resolution would be even larger. We shall address this point later when we discuss the origin of the inhomogeneous broadening.

To check this assignment of broadening types we have conducted a set of far-field PL measurements at various gate voltages and illumination intensities (six laser intensities and 50 gate voltages per laser intensity), and fitted the measured spectra with the double Voigt function discussed above. We have found that throughout the gate voltage range the X^- is well fitted by a Lorentzian (convolved with a Gaussian, which is much narrower than the Lorentzian) while the X lineshape has substantial inhomogeneous Gaussian broadening. These findings are consistent with the results of the near-field measurements.

Let us address the X^- Lorentzian lineshape, which we express as

$$I_{X^-}(E) = \frac{\rho}{(E - E_{\text{peak}}^-)^2 + \Gamma^2}, \quad (1)$$

where E_{peak}^- and Γ are the X^- peak energy and half width at half maximum, respectively. In general, a Lorentzian line is obtained by Fourier transforming an exponentially decaying state, $\Psi(\mathbf{r}) \exp(-\frac{iE_{\text{peak}}^-}{\hbar}t - \frac{\Gamma}{\hbar}t)$, and taking its absolute value squared. Thus, the numerator of the Lorentzian $\rho = \hbar^2 |\Psi(\mathbf{r})|^2$ should depend linearly on the probability density of the state Ψ , and in this particular case, on the X^- density. Since the X^- density should depend linearly on the electron density n_e , we expect

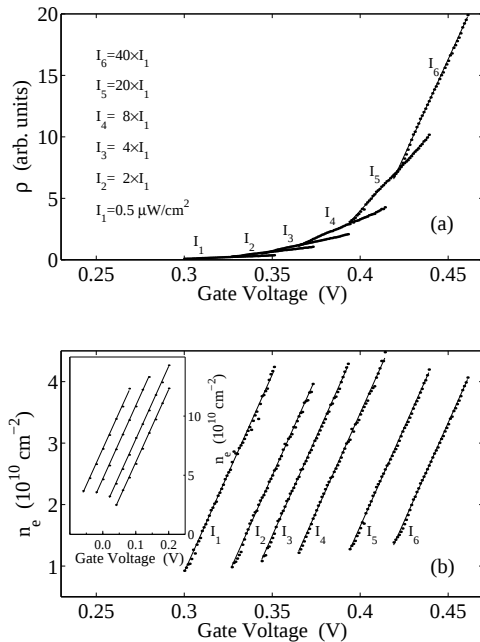


FIG. 2. a) The numerator, ρ , of the X^- Lorentzian as a function of V_g for six laser intensities. b) The electron density n_e as a function of V_g , obtained by applying Eq. (2) to the data of (a). Inset: n_e as a function of V_g obtained from VdP measurements.

that ρ should be linear in n_e . Figure 2a shows ρ (obtained from the fit to the far-field spectra) as a function of the gate voltage, V_g , for different laser intensities. It is clearly seen that ρ depends linearly on V_g , with a slope that increases linearly with laser intensity, I_L . Thus, we can write $\rho = a[V_g - V_0(I_L)]$, where $a = kI_L$. This linear dependence of ρ on V_g is very significant: Using a parallel plate capacitor model for the gated 2DEG we can express the 2DEG density as $n_e = C[V_g - V_0]$, where C is the geometrical capacitance between the Shottkey gate and the 2DEG layer. Hence, we conclude that ρ is indeed proportional to n_e , and we can obtain the 2DEG density by

$$n_e = \rho \frac{C}{a}, \quad (2)$$

and a is simply the slope of the ρ versus V_g curve at some arbitrary laser intensity. This is a new method to extract n_e in the low density regime from the PL data and the geometrical capacitance, without having to measure V_0 and I_L .

To verify the linear dependence of n_e on V_g we measured the conductance using the van der Pauw (VdP) technique [10], under different illumination intensities. The results are shown in the inset of Fig. 2b. Two observations can be made: First, the density does change linearly with gate voltage with a slope C , which is the capacitance per unit area between the Shottkey gate and the 2DEG (the agreement is better than 5%). The second observation is the shift of V_0 to more positive val-

ues with increasing laser intensity. The implication of this behavior is that the electron density in the well is depleted under illumination by an amount that is proportional to the laser intensity, but is independent of the gate voltage. The probable mechanism of this depletion process is tunneling of photo-excited electrons to the surface, leaving the photo-excited holes trapped in the well [12]. The recombination of these holes with the 2DEG electrons results in the reduction of the 2DEG density. In Fig. 2b we apply Eq. (2) to calculate the electron density n_e from the measured values of ρ of Fig. 2a. We get a set of parallel lines similar to those obtained by the VdP measurements. Earlier reports have attempted to extract the electron density from the ratio between the X and X^- intensities [9,13]. We have found that this method does not give an electron density that is linear in V_g . Furthermore, the resulting electron densities are substantially lower than the actual ones.

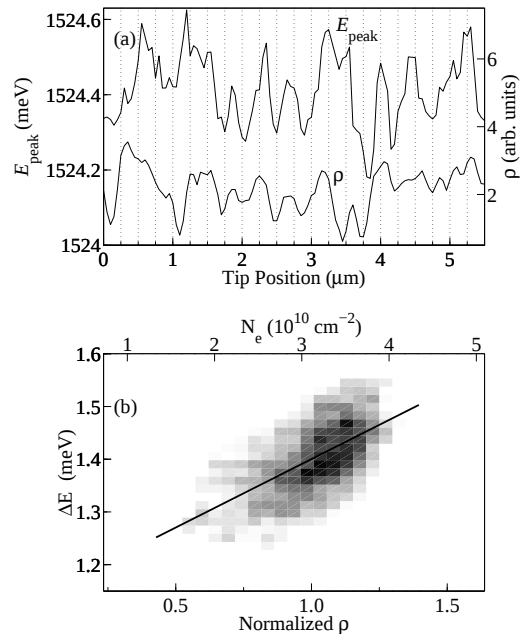


FIG. 3. a) The fluctuations in ρ and in the X peak energy E_{peak} along a line scan of $5.5 \mu\text{m}$ at $n_e = 3.1 \times 10^{10} \text{ cm}^{-2}$. Note the correlation between the two curves. b) A two-dimensional histogram of ρ and E_{peak} for the whole scanned area (~ 3000 points).

Let us try now to understand the origin of the inhomogeneous broadening of the X line. We have shown above that the neutral exciton peak energy, denoted as E_{peak} , exhibits large spatial fluctuations (Fig. 1b). Examining these fluctuations in the near-field spectra, we find that they are strongly correlated with the fluctuations in the X^- intensity, and hence with the local electron density. Figure 3a shows the results of a line scan over $5.5 \mu\text{m}$ with steps of $0.05 \mu\text{m}$. At each spatial point we extract the values of the parameters E_{peak} and ρ . It is clearly seen that the fluctuations in ρ are in phase

with those of E_{peak} : Their minima and maxima occur at nearly the same spatial locations. To determine the relation between the fluctuations in the local density and in the peak energy we plot in Fig. 3b a two-dimensional histogram of the energy difference $\Delta E = E_{\text{peak}} - E_{\text{peak}}^-$ and ρ for all ~ 3000 points in the scanned area at one gate voltage (we normalize ρ by dividing it by its average value). Using Eq. 2 we can relate ρ and n_e , and hence express the horizontal scale in units of electron density (upper axis). The correlation between ΔE and n_e is clearly visible, and emphasized by the line, which is a linear fit for the measured ~ 3000 points. It is important to emphasize that the relation between ΔE and n_e holds locally, regions with high (low) electron density giving rise to large (small) ΔE . Since E_{peak}^- is nearly constant (Fig. 1) the major contribution to the fluctuations in ΔE comes from fluctuations in E_{peak} [14]. We can therefore conclude that the dominant cause of the X inhomogeneous broadening is local density fluctuations. These fluctuations occur on a length scale of the order of the spacer width [4,5], which is smaller than our spatial resolution. Hence, each near-field point unavoidably measures a distribution of electron densities, giving rise to inhomogeneous broadening of the X line already in the near-field spectrum. We note that the broadening of the two-dimensional histogram is independent of n_e , and we believe that it is due to exciton diffusion, characterized by a diffusion length of $\sim 1 \mu\text{m}$: Excitons that are created in a low electron density region may diffuse to a high density region and recombine there.

The dependence of ΔE on n_e was recently a subject of intensive interest. Theoretical analysis predicts that this energy difference should depend on the density as $\Delta E = \mu(n_e) + E_B$, where μ is the 2DEG chemical potential and E_B is the X^- binding energy [15]. This dependence should be understood as follows: When an X^- is neutralized to form an X, the released electron is placed at the chemical potential energy. Hence, the cost in energy of this process is the sum of the binding energy and the chemical potential. This relation was recently studied experimentally [16,17]. It was shown that while it holds at high densities, a weaker dependence of ΔE on n_e is measured in the low density regime [17]. Indeed, the slope of the histogram is smaller by more than a factor of three than that expected from theory. The fact that the far-field inhomogeneous exciton lineshape is directly related to the electron density fluctuations gives a powerful and simple tool for determining these fluctuations.

In conclusion, we have shown that the PL spectrum of a low density 2DEG can be quantitatively understood in terms of the underlying microscopic properties of the 2DEG. We have presented simple and novel methods to extract the average electron density and its fluctuations from the far-field PL spectrum.

This research was supported by the Minerva Foundation. We wish to thank Nanonics for providing the NSOM tips.

-
- [1] K. Kheng *et al.*, Phys. Rev. Lett. **71**, 1752 (1993).
 - [2] G. Finkelstein, H. Shtrikman and I. Bar-Joseph, Phys. Rev. Lett. **74**, 976 (1995).
 - [3] A. J. Shields *et al.*, Phys. Rev. **B51**, 18049 (1995).
 - [4] A.L. Efros, Solid State Commun. **65**, 1281(1988) and **70**, 253 (1989); A.L. Efros, F.G. Pikus, and V.G. Burnett, Phys. Rev. **B47**, 2233 (1993).
 - [5] J.A. Nixon and J.H. Davies, Phys. Rev. **B41**, 7929 (1990).
 - [6] G. Eytan *et al.*, Phys. Rev. Lett. **81**, 1666 (1998).
 - [7] G. Eytan, *et al.*, Ultramicroscopy **83**, 25 (2000).
 - [8] K. Karrai and R. D. Grober, Appl. Phys. Lett. **66**, 1842 (1995).
 - [9] A. Menassen *et al.*, Phys. Rev. **B54**, 10609 (1996).
 - [10] L.J. van der Pauw, Phillips Res. Rep. **13**, 1 (1958).
 - [11] The VdP measurements were performed on a different device, processed from the same wafer. Hence, V_0 is different.
 - [12] S. Glasberg *et al.*, Phys. Rev. **B59**, R10425 (1999).
 - [13] A. Ron *et al.*, Solid State Commun. **97**, 741 (1996).
 - [14] The width of the distribution of ΔE is smaller than that of E_{peak} . This implies that some fluctuations, which are common to X and X^- and do not depend on electron density, were subtracted. The most likely source of these common fluctuations is well width fluctuations.
 - [15] P. Hawrylak, Phys. Rev. **B 44**, 3821 (1991); J. Brum and P. Hawrylak, Comments on Cond. Matt. Phys. **18**, 135 (1997)
 - [16] V. Huard *et al.*, Phys. Rev. Lett. **84**, 187 (2000).
 - [17] G. Yusa, H. Shtrikman, I. Bar-Joseph, to be published in Phys. Rev. **B** (2000).